

# Ferromagnetic transition in a double-exchange system

Mark Auslender<sup>1</sup> and Eugene Kogan<sup>2</sup>

<sup>1</sup> *Department of Electrical and Computer Engineering, Ben-Gurion University of the Negev, P.O.B. 653, Beer-Sheva, 84105 Israel*

<sup>2</sup> *Jack and Pearl Resnick Institute of Advanced Technology, Department of Physics, Bar-Ilan University, Ramat-Gan 52900, Israel*

(February 1, 2008)

We study ferromagnetic transition in three-dimensional double-exchange model. The influence of strong spin fluctuations on conduction electrons is described in coherent potential approximation. In the framework of thermodynamic approach we construct for the system "electrons (in a disordered spin configuration) + spins" the Landau functional, from the analysis of which critical temperature of ferromagnetic transition is calculated.

PACS numbers: 75.10.Hk, 75.30.Mb, 75.30.Vn

## I. INTRODUCTION

The recent rediscovery of colossal magnetoresistance (CMR) in doped Mn oxides with perovskite structure  $R_{1-x}D_xMnO_3$  ( $R$  is a rare-earth metal and  $D$  is a divalent metal, typically Ba, Sr or Ca) [1] substantially increased interest in the double-exchange (DE) model [2,3]. Several approaches were used lately to study the thermodynamic properties of the DE model, including the Dynamical Mean Field Approximation (DMFA) (see [4] and references therein), Schwinger bosons [5], and Variational mean-field approach [6]. Calculated critical temperature  $T_c$  of the ferromagnetic (FM) transition in three-dimensional DE model, surprisingly well agrees with the results of Monte Carlo method [7,6], and high temperature expansion [8] for all values of the itinerant electrons concentration. Still we decided to present our calculation of the  $T_c$ . We believe that our derivation is interesting by itself; it also opens the opportunity for the analysis of the concurrent action of the impurity potential and magnetic disorder [9,10].

## II. HAMILTONIAN AND CPA EQUATIONS

We consider the DE model with the inclusion of the single-site impurity potential. We apply the quasiclassical adiabatic approximation and consider each core spin as a static vector of fixed length  $S$  ( $\mathbf{S}_i = S\mathbf{n}_i$ , where  $\mathbf{n}_i$  is a unit vector). The Hamiltonian of the model  $H([\mathbf{n}_i])$  in site representation is

$$\hat{H}_{ij} = t_{i-j} + (\epsilon_i - J\mathbf{n}_i \cdot \hat{\sigma}) \delta_{ij}, \quad (1)$$

where  $t_{i-j}$  is the electron hopping,  $\epsilon_i$  is the on-site energy,  $J$  is the effective exchange coupling between a core spin and a conduction electron and  $\hat{\sigma}$  is the vector of the Pauli matrices. The hat above the operator reminds that it is a  $2 \times 2$  matrix in the spin space (we discard the hat when the operator is a scalar matrix in the spin space).

The Hamiltonian (1) is random due to randomness of a core spin configuration  $[\mathbf{n}_j]$ ; we also take into account the randomness of the on-site energies  $\epsilon_i$ .

To treat Hamiltonian (1) we use the coherent potential Approximation (CPA) [11–13,9], i.e. we present it as

$$\hat{H} = \overbrace{(t_{i-j} + \hat{\Sigma} \delta_{ij})}^{H^0} + \overbrace{(\epsilon_i - J\mathbf{n}_i \cdot \hat{\sigma} - \hat{\Sigma})}^{\hat{V}} \delta_{ij} \quad (2)$$

(the site independent self-energy  $\hat{\Sigma}(E)$  is to be determined later), and construct a perturbation theory with respect to random potential  $\hat{V}$ . To do this let us introduce the  $T$ -matrix as the solution of the equation

$$\hat{T} = \hat{V} + \hat{V} \hat{G}_0 \hat{T}, \quad (3)$$

where  $\hat{G}_0 = (E - \hat{H}^0)^{-1}$ . For the exact Green function  $\hat{G}$  we get

$$\hat{G} = \hat{G}_0 + \hat{G}_0 \hat{T} \hat{G}_0. \quad (4)$$

The coherent potential approximation (CPA) is expressed by the equation

$$\langle \hat{G} \rangle = \hat{G}_0 \iff \langle \hat{T}_i \rangle = 0, \quad (5)$$

where  $\hat{T}_i$  is the solution of the equation

$$\hat{T}_i = \hat{V}_i + \hat{V}_i \hat{g}(E - \hat{\Sigma}) \hat{T}_i, \quad (6)$$

and

$$g(E) = (G_0(E))_{ii} = \int \frac{N_0(\varepsilon)}{E - \varepsilon} d\varepsilon, \quad (7)$$

where  $N_0(\varepsilon)$  is the bare density of states. Equation for the  $T$ -matrix can be presented as an algebraic equation for the  $2 \times 2$  matrix  $\hat{\Sigma}$ :

$$\left\langle \left[ 1 - \hat{V}_i \hat{g}(E - \hat{\Sigma}) \right]^{-1} \hat{V}_i \right\rangle_{\mathbf{n}, \epsilon} = 0. \quad (8)$$

Eq. (8) coincides exactly with that of Ref. [14].

### III. LANDAU FUNCTIONAL OF A DOUBLE-EXCHANGE SYSTEM

In this part we start from the exact partition function of the system electrons + spins

$$Z = \int \exp \left[ -\beta F_e([\mathbf{n}_j]) + \beta \mathbf{H} \sum_j \mathbf{n}_j \right] D\mathbf{n}_j, \quad (9)$$

where  $N$  is the number of core spins,  $\mathbf{H}$  is magnetic field,  $\beta = 1/T$ , and  $F_e([\mathbf{n}_j])$  is the free energy of the electron subsystem for a given core spin configuration  $[\mathbf{n}_j]$ . Our aim is to obtain Landau functional of the system.

In the mean-field approximation all energy levels depend only upon macroscopic magnetization  $\mathbf{m} = \frac{1}{N} \sum_j \mathbf{n}_j$ . (Mean-field means that we do not take into account large scale fluctuations of macroscopic magnetization, but we certainly take into account microscopic fluctuations of  $\mathbf{n}_i$ .) Hence

$$F_e([\mathbf{n}_j]) \approx F_e(m), \quad (10)$$

and the partition function can be written as

$$Z = \int \exp [-\beta F(\mathbf{m}, \mathbf{H})] d\mathbf{m}, \quad (11)$$

where

$$F(\mathbf{m}, \mathbf{H}) = F_e(m) - N\mathbf{H}\mathbf{m} - TS(m); \quad (12)$$

the quantity

$$S(m) = \ln \int \delta \left( \mathbf{m} - \frac{1}{N} \sum_j \mathbf{n}_j \right) D\mathbf{n}_j \quad (13)$$

is the entropy of the core spin subsystem. We can identify the exponent with the Landau functional of the whole system [15]. Further on we'll be interested in the case  $\mathbf{H} = 0$ ; in this case  $F(\mathbf{m}, \mathbf{H}) = F(m)$ .

At high temperatures the minimum of the functional is at  $m = 0$ . At low temperatures the point  $m = 0$  corresponds to the maximum of the functional. So if we expand  $F_e$  and  $S$  with respect to  $m$

$$\begin{aligned} F_e(m) &= F_0 - F_2 m^2 + \dots \\ S(m) &= S_0 - S_2 m^2 + \dots, \end{aligned} \quad (14)$$

the critical temperature  $T_c$  is found from the equation

$$F_2 = T_c S_2. \quad (15)$$

In fact, we need only the quadratic terms of the Landau functional to find the  $T_c$ .

Here it is appropriate to note that in the approach of Ref. [14] the thermodynamic part of the solution is based on the equation

$$\langle \mathbf{n} \rangle = \int d\Omega_{\mathbf{n}} P(\mathbf{n}) \mathbf{n}, \quad (16)$$

where  $P(\mathbf{n})$  is the Boltzmann factor for a spin, determined from the DMFA ansatz.

To calculate the entropy we expand the  $\delta$ -function in Eq. (13) in Fourier integral

$$\delta \left( \mathbf{m} - \frac{1}{N} \sum_j \mathbf{n}_j \right) \sim \int e^{i(N\mathbf{m} - \sum_j \mathbf{n}_j) \cdot \mathbf{r}} d\mathbf{r}, \quad (17)$$

which gives an opportunity to calculate integrals with respect to  $D\mathbf{n}_j$ . After simple algebra we obtain (ignoring irrelevant multipliers in the argument of the logarithm)

$$S(m) = \ln \left\{ (4\pi)^N \int_0^\infty \sin(Nrm) \left( \frac{\sin r}{r} \right)^N r dr \right\}. \quad (18)$$

Calculated integral by the steepest descent method, up to the terms of order of  $m^2$  we obtain

$$S = N \left[ \ln(4\pi) - \frac{3m^2}{2} \right]. \quad (19)$$

The grand canonical potential for the electron subsystem is

$$-\beta\Omega(\mu, m) = \frac{N}{\pi} \int_{-\infty}^{+\infty} \ln [1 + e^{-\beta(E-\mu)}] \text{Im } g_c(E) dE, \quad (20)$$

where  $g_c$  is the charge locator  $g_c = \text{Tr } \hat{g}$ . The free energy is

$$F_e(N, m) = \Omega(\mu, m) + \mu N; \quad (21)$$

the connection between the number of holes per site  $x$  and chemical potential  $\mu$  is given by the equation

$$1 - x = \frac{1}{\pi} \int_{-\infty}^{\infty} f(E) \text{Im } g_c(E) dE, \quad (22)$$

where  $f(E)$  is the Fermi distribution function.

The calculation is especially simple, when we can consider the electron gas as degenerate and ignore the terms of order of  $T/\mu$  (that is we can consider the temperature of electron gas as being effectively equal to zero). In this case

$$F_e = \frac{N}{\pi} \int_{-\infty}^{\mu} E \text{Im } g_c(E) dE. \quad (23)$$

Expanding  $g_c$  with respect to  $m$

$$g_c = g_0 + g_2 m^2 + \dots, \quad (24)$$

we obtain

$$F_2 = \frac{N}{\pi} \int_{-\infty}^{\mu_0} (\mu_0 - E) \text{Im } g_2(E) dE, \quad (25)$$

where  $\mu_0$  is found from the equation

$$1 - x = \frac{1}{\pi} \int_{-\infty}^{\mu_0} \text{Im } g_0(E) dE. \quad (26)$$

#### IV. $T_C$ FOR SEMI-CIRCULAR DENSITY OF STATES

We consider semi-circular (SC) bare (i.e. for  $\epsilon \equiv 0$  and  $J = 0$ ) DOS

$$N_0(\epsilon) = \frac{2}{\pi W} \sqrt{1 - \left(\frac{\epsilon}{W}\right)^2}, \quad (27)$$

at  $|\epsilon| \leq W$  and  $N_0(\epsilon) = 0$  otherwise, for which

$$g(E) = \frac{2}{W} \left[ \frac{E}{W} - \sqrt{\left(\frac{E}{W}\right)^2 - 1} \right]. \quad (28)$$

Hence we obtain

$$\hat{\Sigma} = E - 2w\hat{g} - \hat{g}^{-1}, \quad (29)$$

where  $w = W^2/8$ . Thus, Eq. (8) can be presented as

$$\hat{g} = \left\langle (E - \epsilon + J\mathbf{n}\sigma - 2w\hat{g})^{-1} \right\rangle_{\mathbf{n},\epsilon}. \quad (30)$$

It is convenient to write the locator  $\hat{g}$  in the form

$$\hat{g} = \frac{1}{2}(g_c\hat{I} + \mathbf{g}_s\hat{\sigma}), \quad (31)$$

where  $\hat{I}$  is a unity matrix. For the charge locator  $g_c$  and spin locator  $\mathbf{g}_s$  we obtain the system of equations

$$\begin{aligned} g_c &= 2 \left\langle \frac{E - 2wg_c}{(E - \epsilon - wg_c)^2 - (J\mathbf{n} + w\mathbf{g}_s)^2} \right\rangle_{\mathbf{n},\epsilon} \\ \mathbf{g}_s &= 2 \left\langle \frac{J\mathbf{n} + w\mathbf{g}_s}{(E - \epsilon - wg_c)^2 - (J\mathbf{n} + w\mathbf{g}_s)^2} \right\rangle_{\mathbf{n},\epsilon}. \end{aligned} \quad (32)$$

In the strong Hund coupling limit ( $J \rightarrow \infty$ ) we obtain from Eqs. (32) two decoupled spin sub-bands. For each sub-band, after shifting the energy by  $\pm J$  we obtain

$$\begin{aligned} g_c &= \left\langle \frac{1}{E - \epsilon - wg_c - wn^z g_s} \right\rangle_{\mathbf{n},\epsilon} \\ g_s &= \left\langle \frac{n^z}{E - \epsilon - wg_c - wn^z g_s} \right\rangle_{\mathbf{n},\epsilon}, \end{aligned} \quad (33)$$

where  $\mathbf{g}_s = (0, 0, g_s)$  (axis OZ is directed along  $\mathbf{m}$ ).

For a saturated FM phase ( $m = 1$ ), we obtain  $g_s = g_c$ , and closed equation for the charge locator is

$$g_c = \left\langle \frac{1}{E - \epsilon - 2wg_c} \right\rangle_{\epsilon}. \quad (34)$$

For a paramagnetic (PM) phase ( $m = 0$ ), we obtain  $\mathbf{g}_s = 0$ , and closed equation for the charge locator  $g_c(m = 0) \equiv g_0$  is

$$g_0 = \left\langle \frac{1}{E - \epsilon - wg_0} \right\rangle_{\epsilon}. \quad (35)$$

In both cases only the averaging with respect to random on-site energies is left. So, the DOS in PM phase is equal to the DOS in FM phase of another model, with decreased by a factor of  $\sqrt{2}$  bare bandwidth.

From here on we ignore the on-site energies disorder and put  $\epsilon \equiv 0$ . In this case the solution of Eq. (35) for  $g_0$  coincides with Eq. (28), with  $W/\sqrt{2}$  substituting for  $W$ . Expanding Eq. (33) with respect to  $m$  we obtain the system

$$\begin{aligned} g_2 m^2 &= g_0^2 (wg_2 + mwg_s) + g_0^3 \frac{w^2}{3} g_s^2, \\ g_s &= mg_0 + g_0^2 \frac{w}{3} g_s. \end{aligned} \quad (36)$$

Substituting the value of  $g_2$  into Eq. (25), we obtain the critical temperature:


$$T_c = \frac{2w}{3\pi} \int_{-\infty}^{\mu_0} (\mu_0 - E) \text{Im} \left[ \frac{g_0^3}{(1 - wg_0^2)(1 - \frac{w}{3}g_0^2)^2} \right] dE. \quad (37)$$

Calculated integral analytically, we get for the  $T_c$ :

$$T_c = \frac{\sqrt{2}}{4\pi} \left[ \sqrt{1 - y^2} - \frac{1}{\sqrt{3}} \tan^{-1} \sqrt{3(1 - y^2)} \right] W \quad (38)$$

where the reduced chemical potential  $y = \sqrt{2}\mu_0/W$  is found from the equation

$$x = \frac{1}{2} - \frac{1}{\pi} \left[ \sin^{-1} y + y\sqrt{1 - y^2} \right]. \quad (39)$$

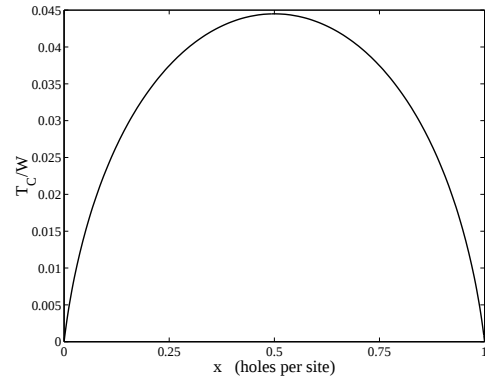

**Fig. 1.** The calculated Curie temperature for the semi-circular DOS at  $J = \infty$  as function of hole concentration  $x$ .

One notices the particle-hole symmetry, namely  $T_c(x) = T_c(1 - x)$ . At  $x \rightarrow 0$  and  $x \rightarrow 1$ ,  $T_c \rightarrow 0$ . The optimal doping turns out to be 0.5, with  $T_c = 0.045W$ .

## V. DISCUSSION

Any calculation of the  $T_c$  in the DE model includes, on one hand, calculation of the energy of electron interacting with randomly directed core spins, and, on the other hand, the analysis of phase transition in the system of spins with the interaction inferred from the solution of the electron part of the problem. The difference between our approach and that of Ref. [14], is similar to the difference between the two mean-field approximations for the Heisenberg model: one based on the analysis of a local spin in a coherent field, which by itself depends upon the averaged magnetization, the other based on the expansion of the partition function [11,15]. For the Heisenberg model the two approaches give exactly the same result. This turned out to be the case also the case for the DE model. Our result for the  $T_c$  (Eq. (37)), using integration by parts, can be exactly reduced to Eq. (49) of Ref. [14], which in our notation is

$$T_c = \frac{2w}{3\pi} \int_{-\infty}^{\mu_0} \text{Im} \left[ \frac{g_0^2}{1 - \frac{w}{3} g_0^2} \right] dE. \quad (40)$$

The result of Refs. [5] for the  $T_c$  in our notation is

$$T_c = \frac{\sqrt{2}}{9\pi} (1 - y^2)^{3/2} W. \quad (41)$$

It is close to our result numerically, but the functional dependence of the  $T_c$  upon hole concentration is essentially different. The difference comes from our use of the CPA for the description of electrons, in distinction from the mean-field decoupling of charge and core spin fluctuations in de Gennes' spirit, used in Refs. [5]. (In the part of Refs. [5] where the charge-spin coupling is taken into account, the explicit result for the  $T_c$  is not presented.)

The DE scenario of the FM transition in manganites attracted especial attention after its validity was questioned in Ref. [16]. In the following discussion, the position of one side can be expressed by reformulation of the rhetorical question by Hubbard [17]: "How, in the itinerant model, explain a Curie temperature  $\sim 1000^\circ$  for iron, when calculations always give an exchange field  $\sim 1 - 2$  eV?" in the form: How, in the DE model, explain a Curie temperature  $\sim 300^\circ$  for a manganite (at optimal doping), when calculations always give a bandwidth  $\sim 1 - 2$  eV? The fallacy is based on the implicit assumption that the  $T_c$  should be of the order of the energy difference between the fully ordered FM state and the paramagnetic state (which is the smallest of the band width and the exchange integral). It does not take into account that the

fluctuations which restore magnetic symmetry in itinerant models are local fluctuations in the orientation of magnetic moments, with much lower energy [17]. That is why the numerical coefficient in Eq. (38) turns out to be much less than one.

## VI. ACKNOWLEDGMENT

We are thankful for helpful comments to J.L. Alonso, L.A. Fernandez, G. Gomes-Santos, F. Guinea, V. Laliena and V. Martin-Mayor. This research was supported by the Israeli Science Foundation administered by the Israel Academy of Sciences and Humanities.

- 
- [1] R. von Helmolt *et al.*, Phys. Rev. Lett. **71**, 2331 (1993); K. Chandra *et al.*, Appl. Phys. Lett. **63**, 1990 (1993); S. Jin *et al.*, Science **264**, 413 (1994).
  - [2] C. Zener, Phys. Rev. **82**, 403 (1951).
  - [3] P. W. Anderson and H. Hasegawa, Phys. Rev. **100**, 675 (1955).
  - [4] N. Furukawa: in *Physics of Manganites*, ed. T. Kaplan and S. Mahanti (Plenum Publishing, New York, 1999).
  - [5] D. P. Arovas, G. Gomes-Santos, F. Guinea, Phys. Rev. B **59**, 13569 (1999); F. Guinea, G. Gomes-Santos, D. P. Arovas, Phys. Rev. B **62**, 391 (2000).
  - [6] J. L. Alonso, L. A. Fernandez, F. Guinea, V. Laliena, and V. Martin-Mayor, Phys. Rev. B **63**, 054411 (2001).
  - [7] Y. Motome and N. Furukawa, J. Phys. Soc. Jpn. **69**, 3785 (2000).
  - [8] H. Röder, R. R. P. Singh, and J. Zang, Phys. Rev. B **56**, 5084 (1997).
  - [9] M. Auslender and E. Kogan, Eur. Phys. J. B, (2001); cond-mat/0006184.
  - [10] M. Auslender and E. Kogan, to be published.
  - [11] J. M. Ziman, Models of Disorder, Cambridge University Press, 1979.
  - [12] P. Soven, Phys. Rev. **156**, 809 (1967); D. Taylor, Phys. Rev. **156**, 1017 (1967).
  - [13] A. Rangette, A. Yanase, and J. Kubler, Solid State Comm. **12**, 171 (1973); K. Kubo, J. Phys. Soc. Japan **36**, 32 (1974).
  - [14] N. Furukawa, cond-mat/9812066.
  - [15] J. F. Negele and H. Orland, *Quantum Many-Particle Systems* (Perseus Books, Reading MA, 1998).
  - [16] A. J. Millis, P. B. Littlewood, and B. I. Shraiman, Phys. Rev. Lett. **74**, 5144 (1995).
  - [17] J. Hubbard, Phys. Rev. B **19**, 2626 (1979).